

New Specification for Internal Liquid Epoxy Coating Systems For Carbon Steel Pipes and Line Pipes

Amal Al-Borno, Ph.D.

Mick Brown, Ph.D.

Charter Coating Services (2000) Ltd.

#6, 4604-13 Street N.E.

Calgary, Alberta, Canada T2E 6P1



Talal Nabhani, Ph.D.

Nasser Behlani, Eng

Ahmed Al-Harthy, Eng.

Johnson Barry, Eng.

Petroleum Development Oman

PO Box 81, Postal Code 113

Muscat, Sultanate of Oman



شركة تنمية نفط عُمان

Petroleum Development Oman

Project Background – Internal Pipe Coatings



Problem:

- Shortage of local FBE applicators for Oman
- Projects not being done to schedule
- No documentation for qualification of alternative coatings

Project:

- Prepare specifications for liquid coating
- Market research liquid coatings
- Identify, source and test candidate coatings

Liquid Coatings vs. FBE



FBE

- base and converter together
- high application temperatures
- phosphate steel treatment sometimes recommended
- DSC useful as QC tool
- powder application equipment required
- typically very fast cure of coating
- usually very flexible

Liquid Coatings

- base and converter separate
- application temperatures lower than for FBE
- phosphate treatment not required
- DSC not such a QC tool
- variable and different application equipment used
- typically require longer time to cure coating
- often less flexible than FBE

Operating Conditions



Parameter	System 1 (water only)	System 2 (Production fluids containing oil, gas and water)
Design Temp.	85 °C	85 °C
Design Pressure	Not Applicable	50 bar
GOR	0	<300
% Water Cut	Not Applicable	50%
CO₂ Pp	Not Applicable (0)	3 bar
H₂S Pp	Not Applicable (0)	0.5 bar
Solid/Velocity	Less than erosional velocity	Less than erosional velocity
Chlorides (Cl⁻)	<100000 ppm	<100000 ppm

Market Research for Coatings

- 40 coating companies were contacted



Market Research for Coatings – contd.

- Only 8 suppliers indicated that they had appropriate coatings
- 10 coatings were proposed
- Study of product data sheets and test data resulted in elimination of 4 products
- Only 6 products for initial testing!

From...



Specification - objectives



Specification details to cover:

- define responsibilities of end-user, supplier and applicator
- qualification procedures for coating and applicator
- application process details
- QC of materials and equipment
- inspection requirements and procedures
- coating tests for qualification and QC/QA

Qualification of Coatings



- consider factors in service conditions that are most likely to lead to coating failure
- tests to demonstrate performance \geq FBE for service conditions
- develop screening tests to eliminate inappropriate coatings
- market research available liquid coatings
- identify and source candidate coatings
- develop test program for screening and qualification
- conduct testing to qualify coatings

Qualification Testing



- To ensure good performance and \geq FBE in the service conditions, a broad spectrum of tests were selected
- Tests include destructive and NDT with the latter particularly suitable for QC on site
- Tests examine properties related to the application on steel and also coating properties

Physical Properties Tests



- Film Thickness – how evenly was it applied and how well does it cover the surface?
- Holiday detection – are there holes or cracks in the coating?
- Hardness – how hard is the coating?
- Porosity – what level of foam is present in the coating film near the substrate and in cross section?
- Interface contamination – how clean was the steel surface when the coating was applied?

Physical Performance



- Impact – how well does the coating resist damage when impacted?
- Flexibility – how well will it cope with bending of the pipeline?
- Abrasion – how well does the coating resist film loss when abraded?
- Penetration – how much does the film thickness reduce under a heavy localized load?

Physical Characteristics



Adhesion and coating integrity:

- Knife adhesion – leverage at base of coating particularly examines adhesion to substrate.
- Pull-off adhesion – examines adhesive and cohesive properties of the coating; shows any weak regions in the coating film.

Note that these tests are also used after immersion tests to examine for changes in the coating film as a result of the testing

Physical Characteristics



Barrier properties and effects of heat:

- Water vapour transmission – how good is the coating as a barrier to the passage of water?
- DSC – is the T_g above the pipeline rated temperature and does it agree with data sheet?
- Linear thermal expansion – what happens to film dimensions when the temperature changes and how does this compare to steel?

Chemical Resistance Tests



- Hot water resistance (85°C) – how well does the coating retain adhesion when immersed?
- Chemical resistance + autoclave – this test exposes the coating to different chemicals for 90 days and then exposes the coating to pressure and high temperature before examining for blisters, cracks, delamination, or other defects.

Chemical Resistance Tests



- CD (85°C) – how does cathodic protection affect coating adhesion?
- Water absorption (23 and 85°C) – how much water will the coating absorb with long-term immersion?
- Gas pressure variation (10 cycles) – how well does the coating withstand changes in pressure?
- Salt fog – how well does the coating withstand high salt environments and how well does it hinder undercreep?

Screening Tests




- In order to minimize the testing conducted, the candidate coatings were initially only tested using selected tests.
- Based on the results in these screening tests coatings were selected for testing in the remaining qualification tests.


Screening Tests - Adhesion



Pull-Off Adhesion

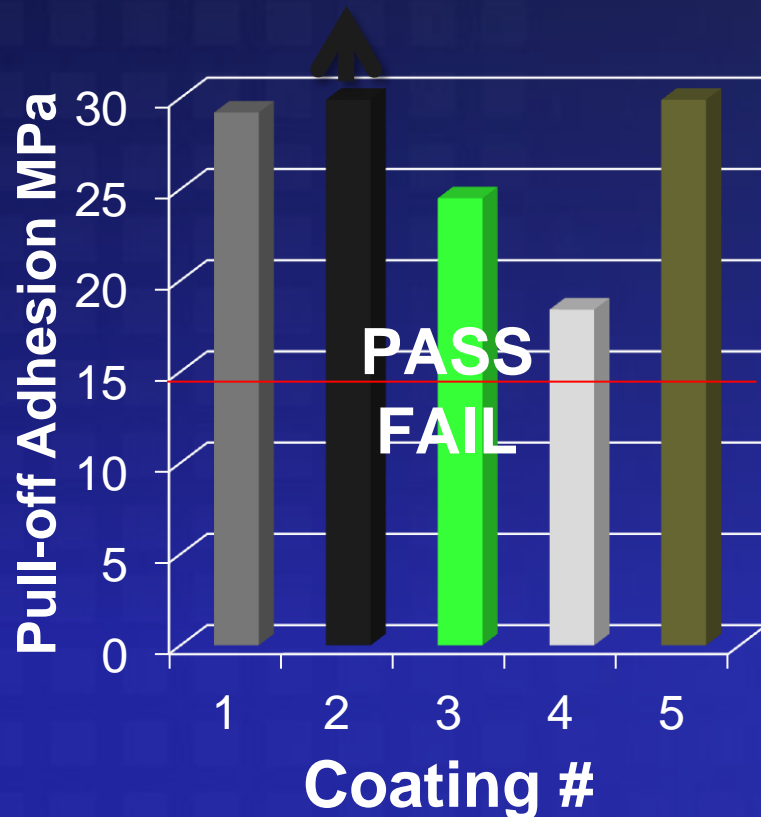


X-Scribe Adhesion

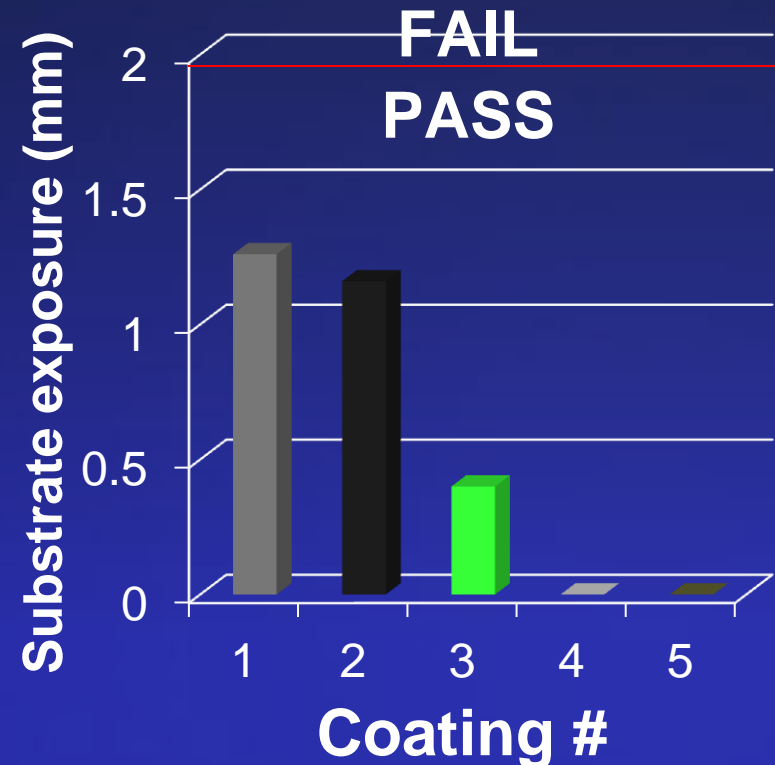


- All coatings showed very good adhesion to the steel and passed Specification requirements

Screening Tests - Flexibility

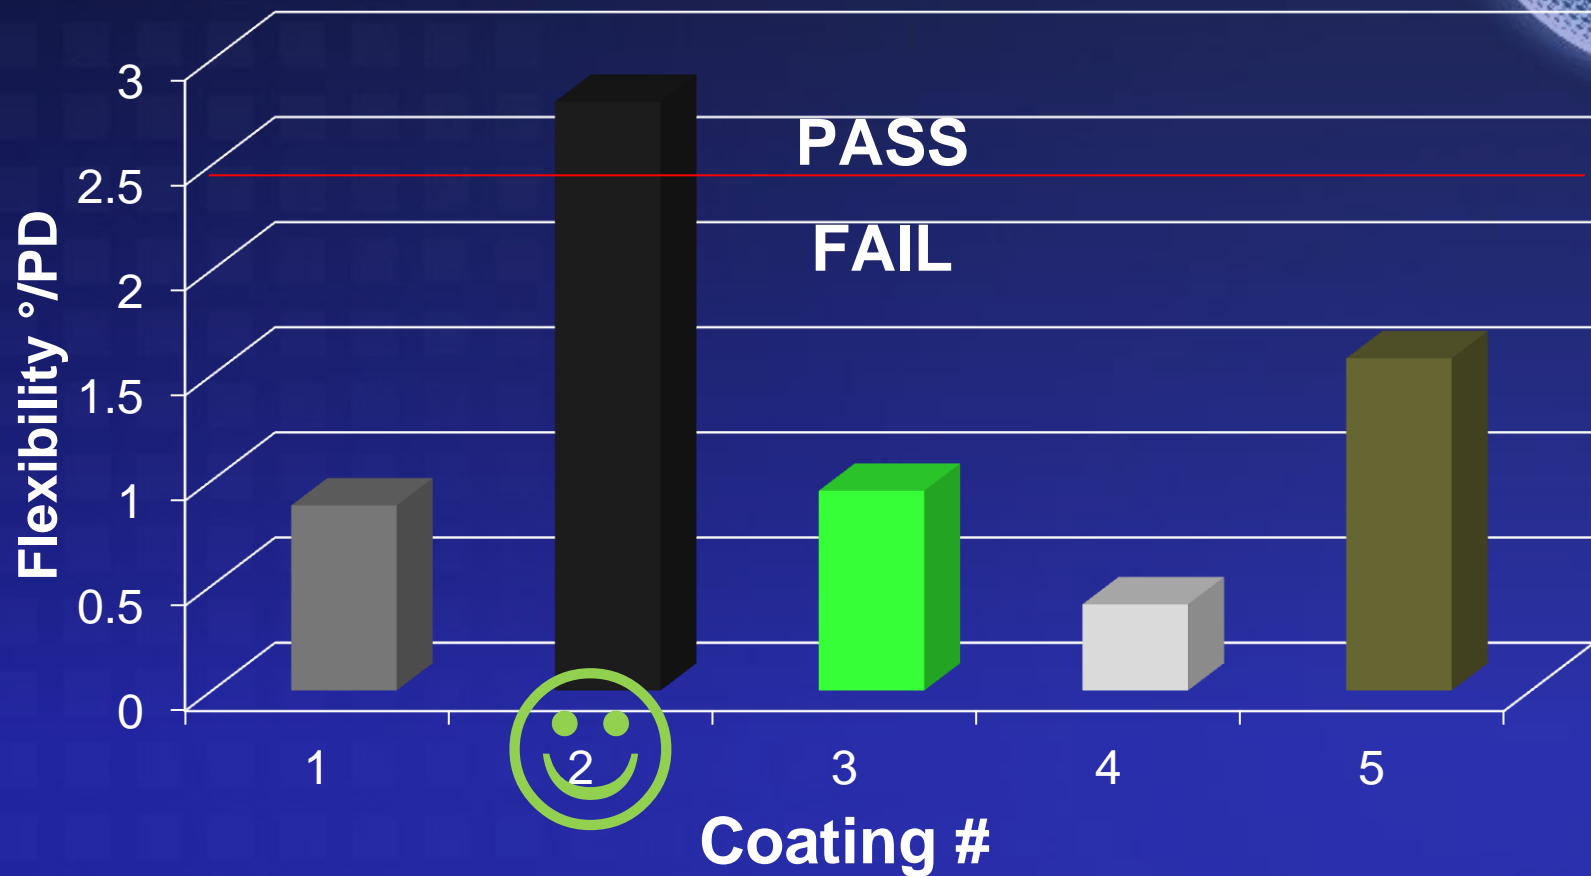

- Only Coating 2 passed the test, Coating 5 was next best and Coating 4 was the least flexible

Screening - Cathodic Disbondment

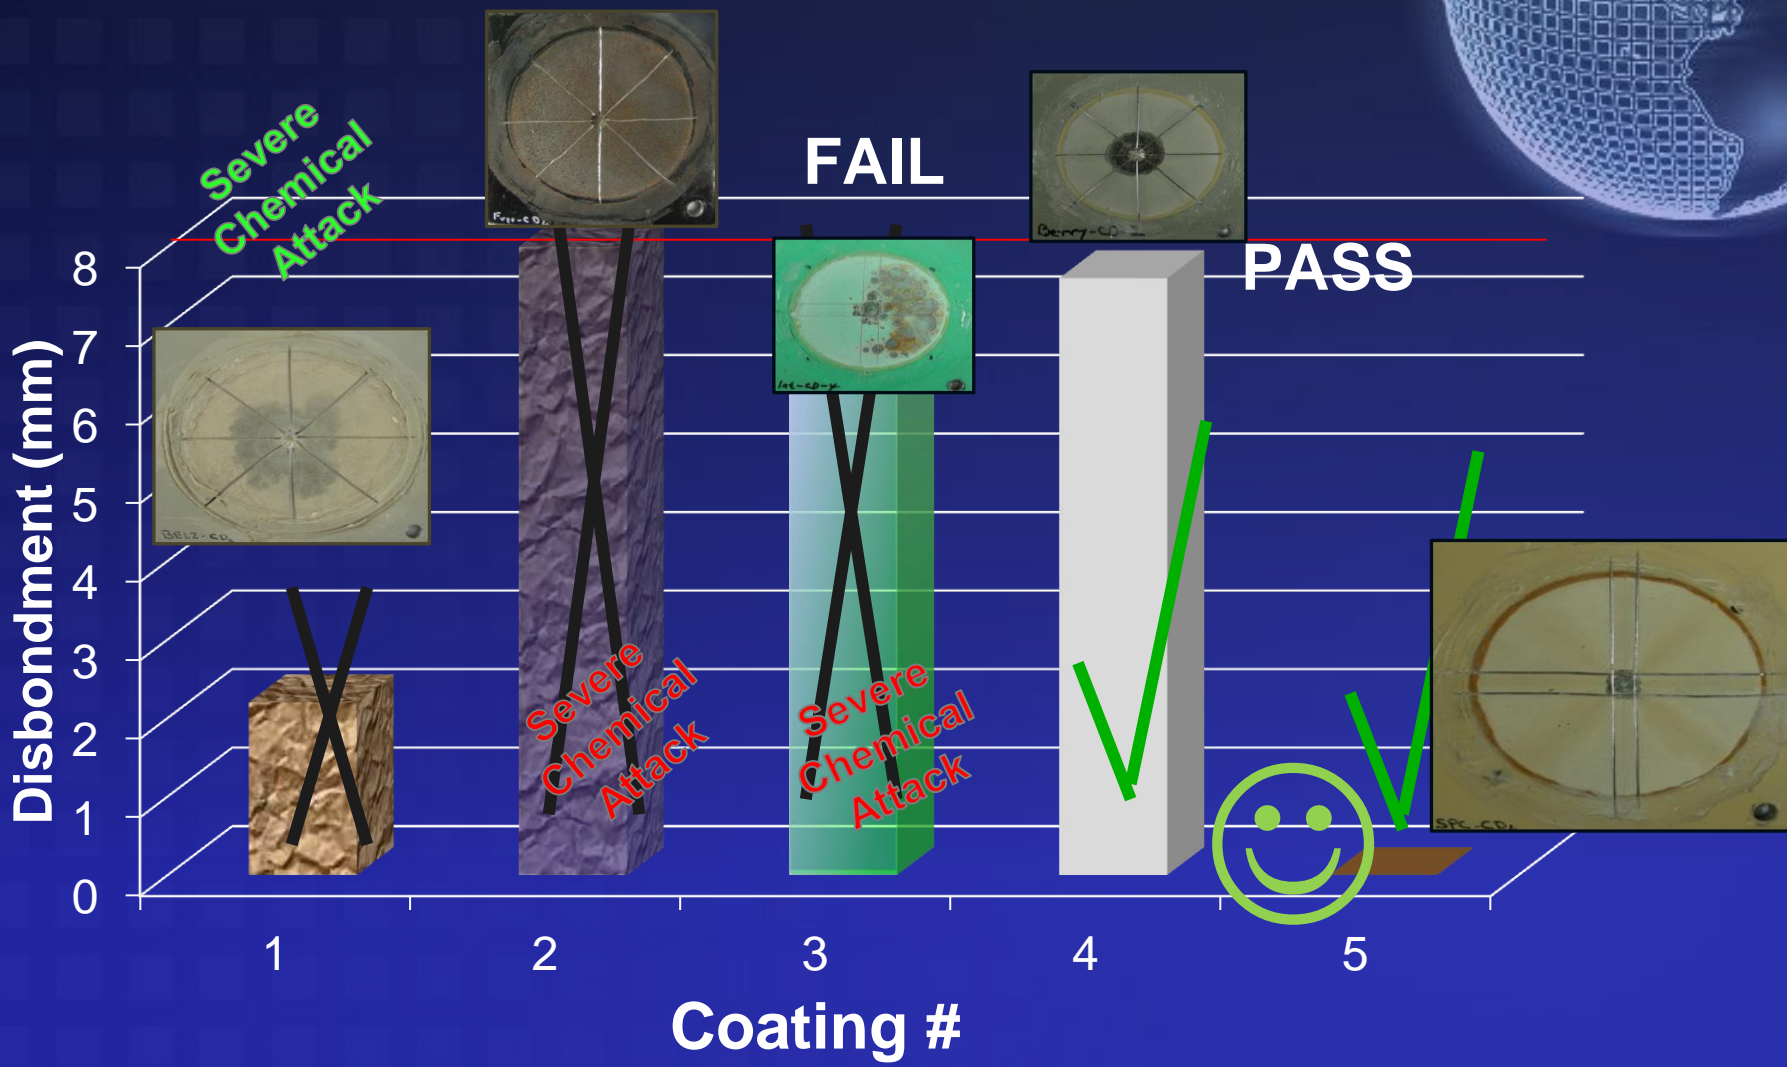

- Coatings 1, 2 and 3 had severe chemical attack but Coatings 4 and 5 passed with Coating 5 best

Screening Tests - Autoclave



- Coatings 1, 2, 4, and 5 had excellent resistance with no blisters, no adhesion loss, & only slight color change.
- Coating 3 blistered in both phases



Gas Phase

Water Phase

1

2

3


4

5


Coating #

Screening Tests - Water Vapor Transmission

Test at 85°C

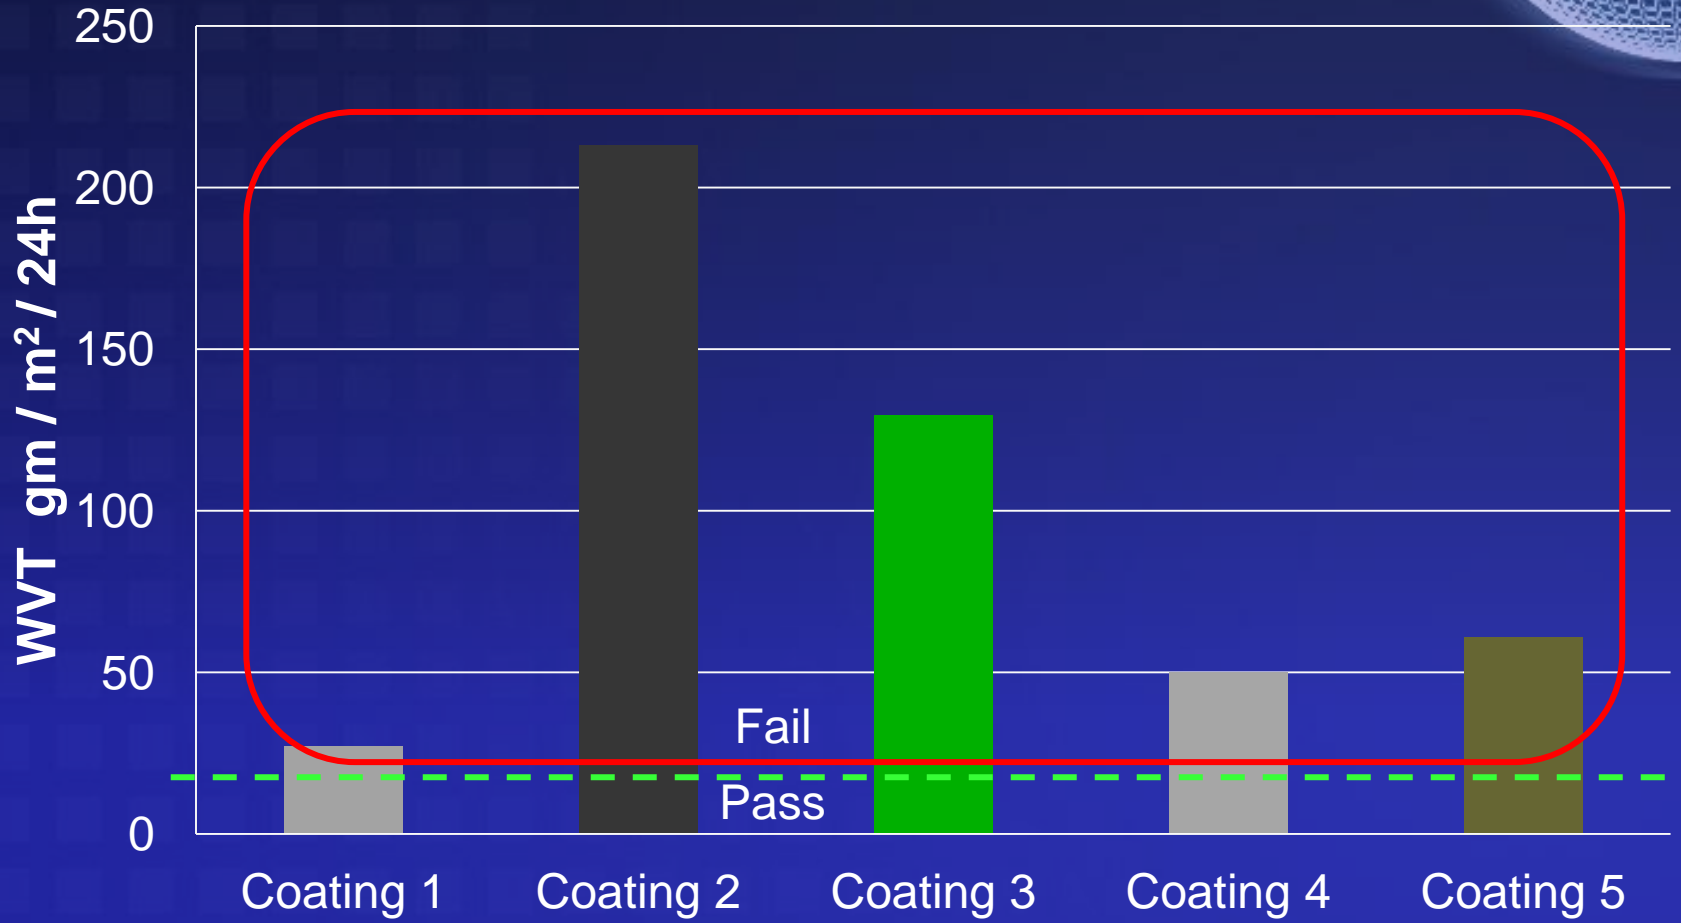

Screening Tests - Water Absorption

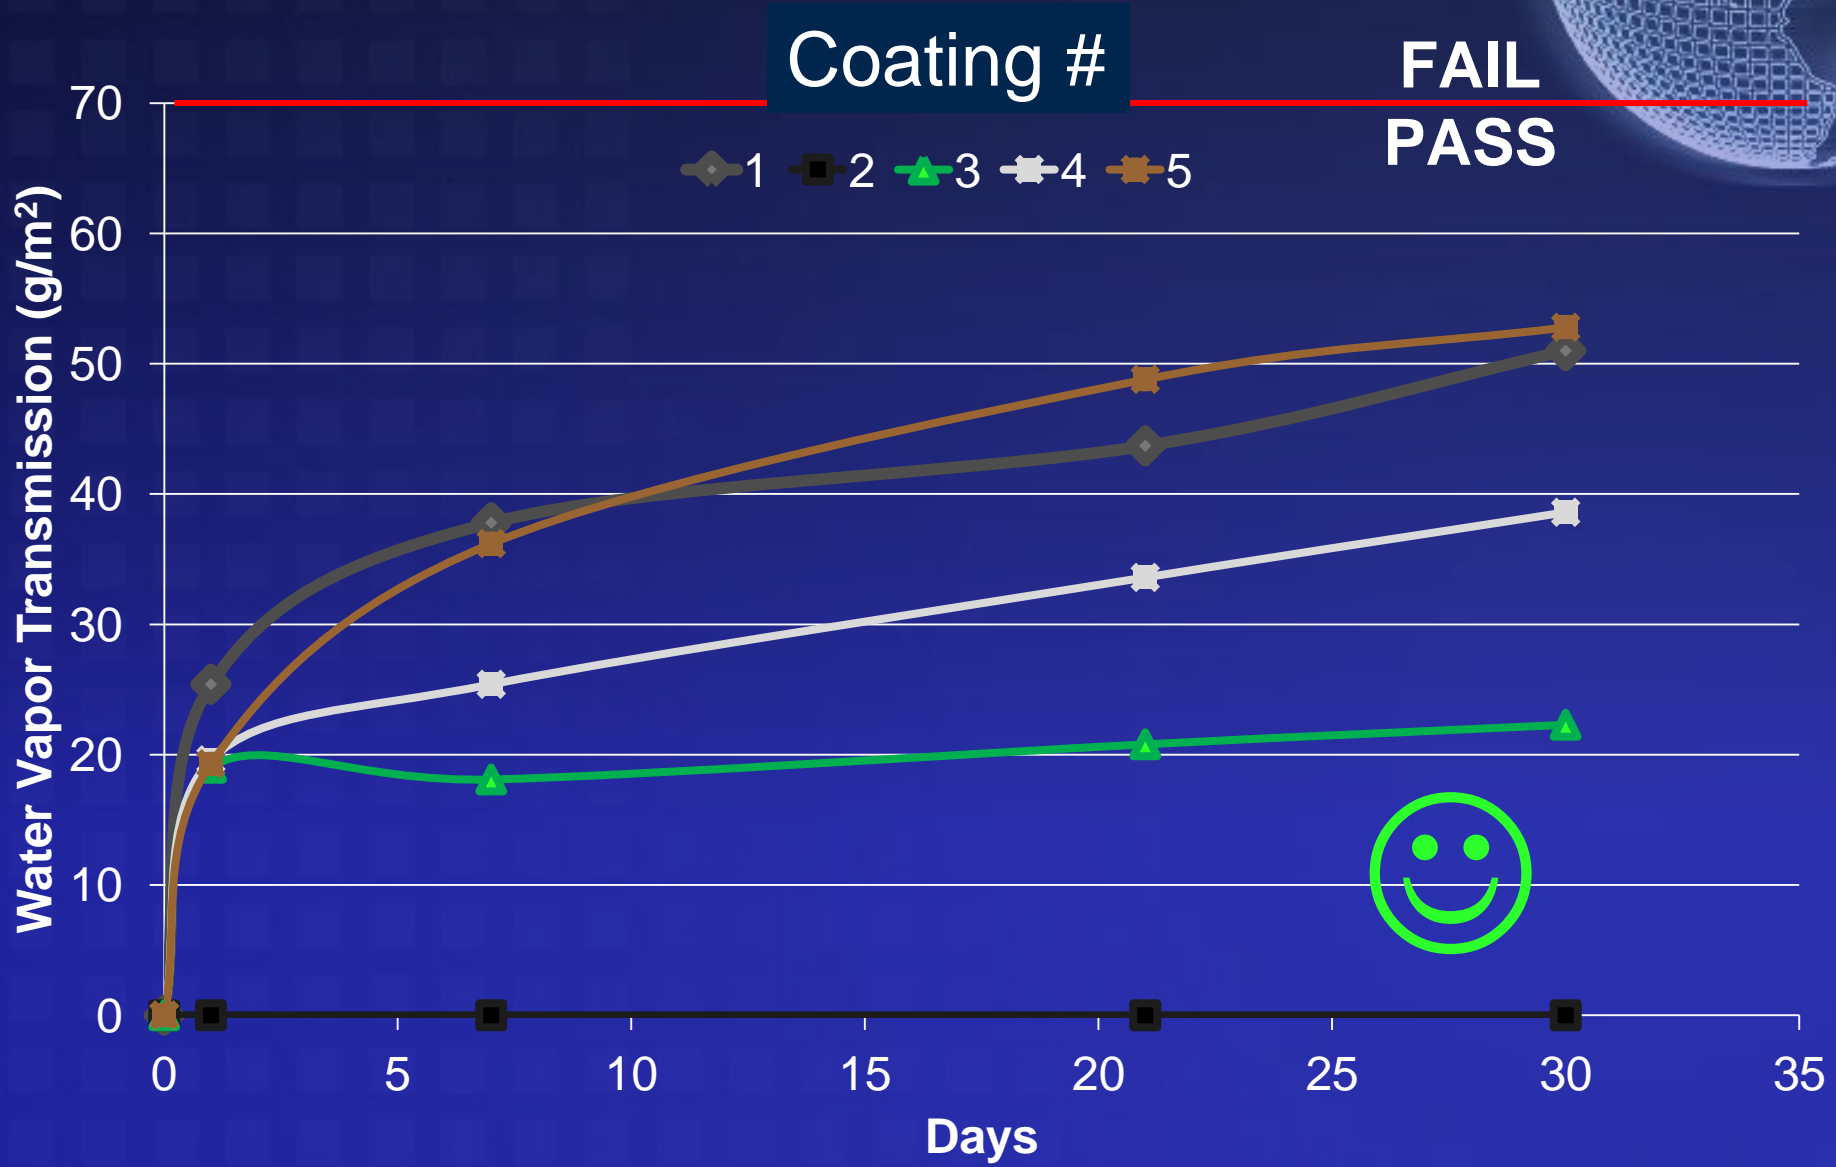

Comparison Table

Test	Coating 1	Coating 2	Coating 3	Coating 4	Coating 5
Adhesion					
Flexibility					
Porosity					
CD Test					
Autoclave					
WVT					
Water Absorption					

Screening Test Conclusions



- Although all coatings were epoxy novalac based, there were large differences in performance
- Coatings 4 & 5 were selected for further qualification testing

Coatings 4 & 5 Qualification Testing



Additional tests conducted:

- WVT and water absorption extension to 90days
- Hot water resistance: 85°C for 90 days
- Penetration: 85°C
- Impact resistance: 0 and 20°C
- Abrasion resistance: 23°C
- Chemical resistance: 23°C for 90 days
- Autoclave after chemical resistance
- Gas pressure variation: 23°C at 100 bar, 10 cycles
- Salt fog: 35°C for 1000 hours
- DSC
- Linear Thermal Expansion: -10°C to + 90°C

Coatings 4 & 5 Qualification Testing



Following are highlights of performance and differences.

Note the following:


- Hot water resistance: both passed well
- Penetration: both passed well
- Gas pressure variation: both passed well
- Salt fog: both passed well
- Other tests are summarized on following slides...

Water vapour transmission (WVT)



WVT at 23°C
met requirement
of $\leq 3.0 \text{ g/m}^2/24\text{h}$

At 85°C neither
coating met
requirement but test
vessel could not
handle pressure at
elevated temp.

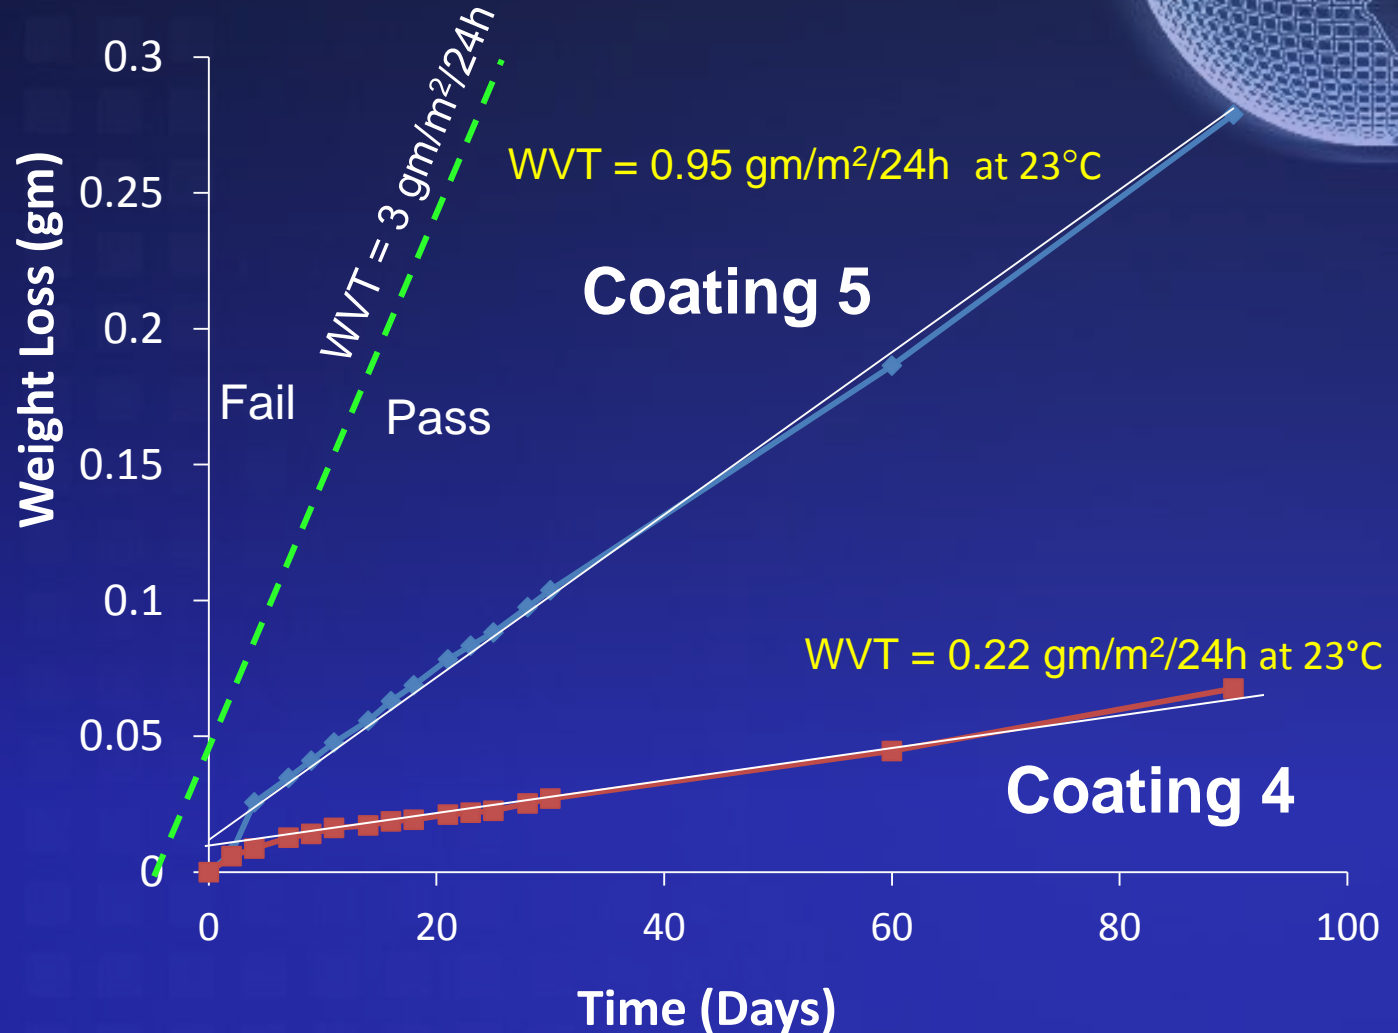


WVT = $0.95 \text{ gm/m}^2/24\text{h}$ at 23°C

Coating 5


WVT = $0.22 \text{ gm/m}^2/24\text{h}$ at 23°C

Coating 4


Water absorption

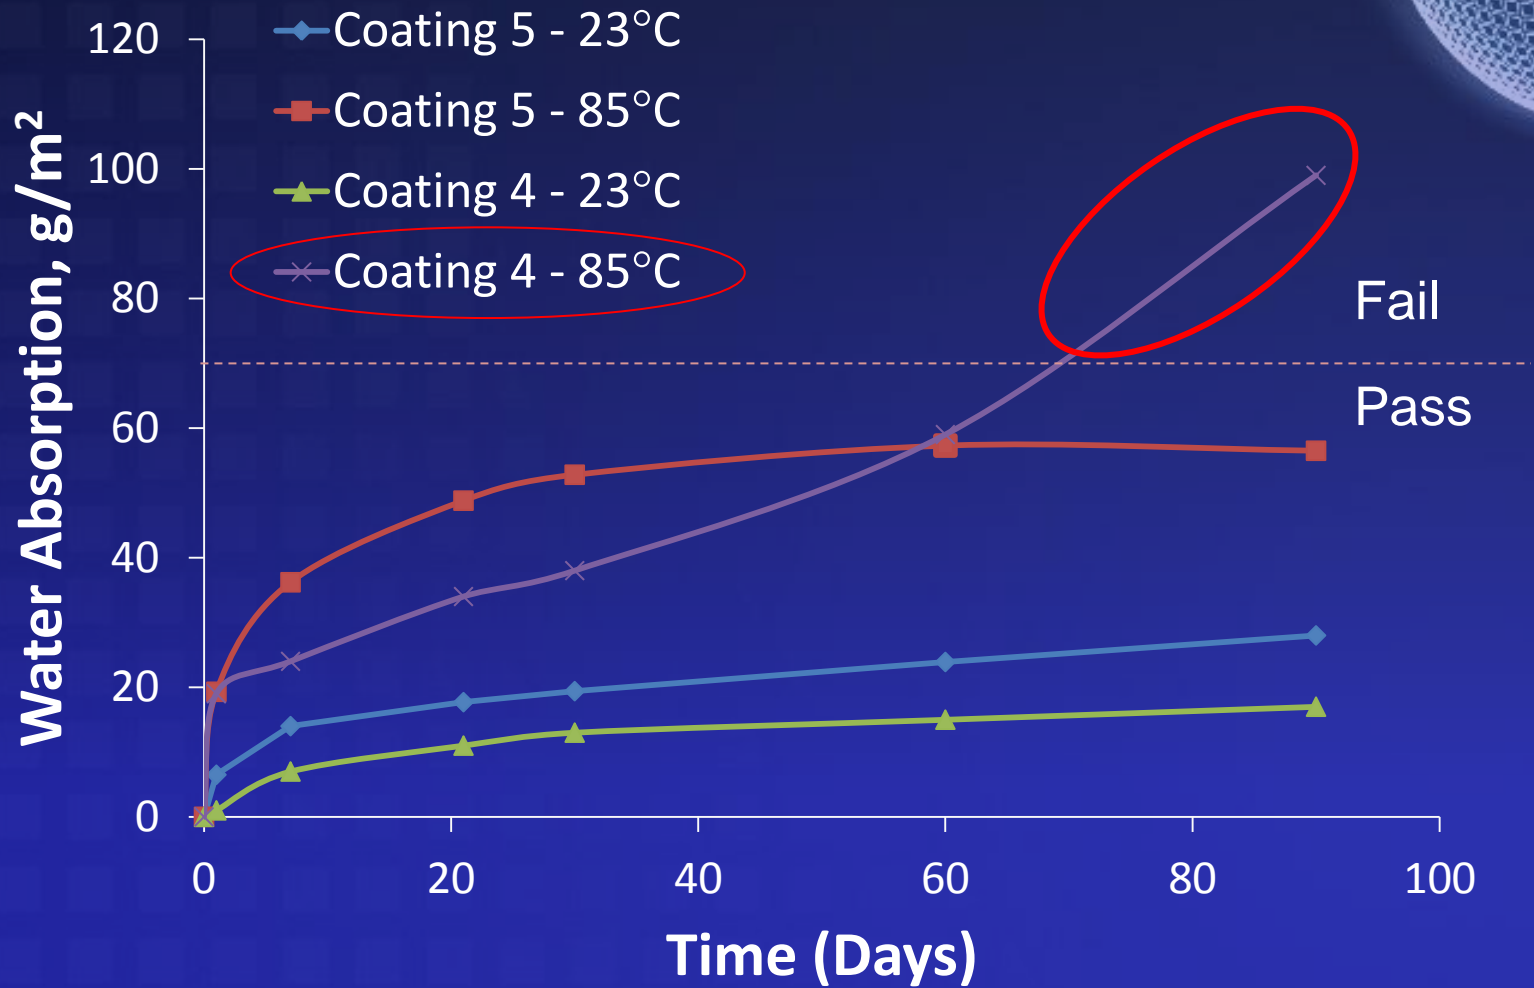

Impact resistance

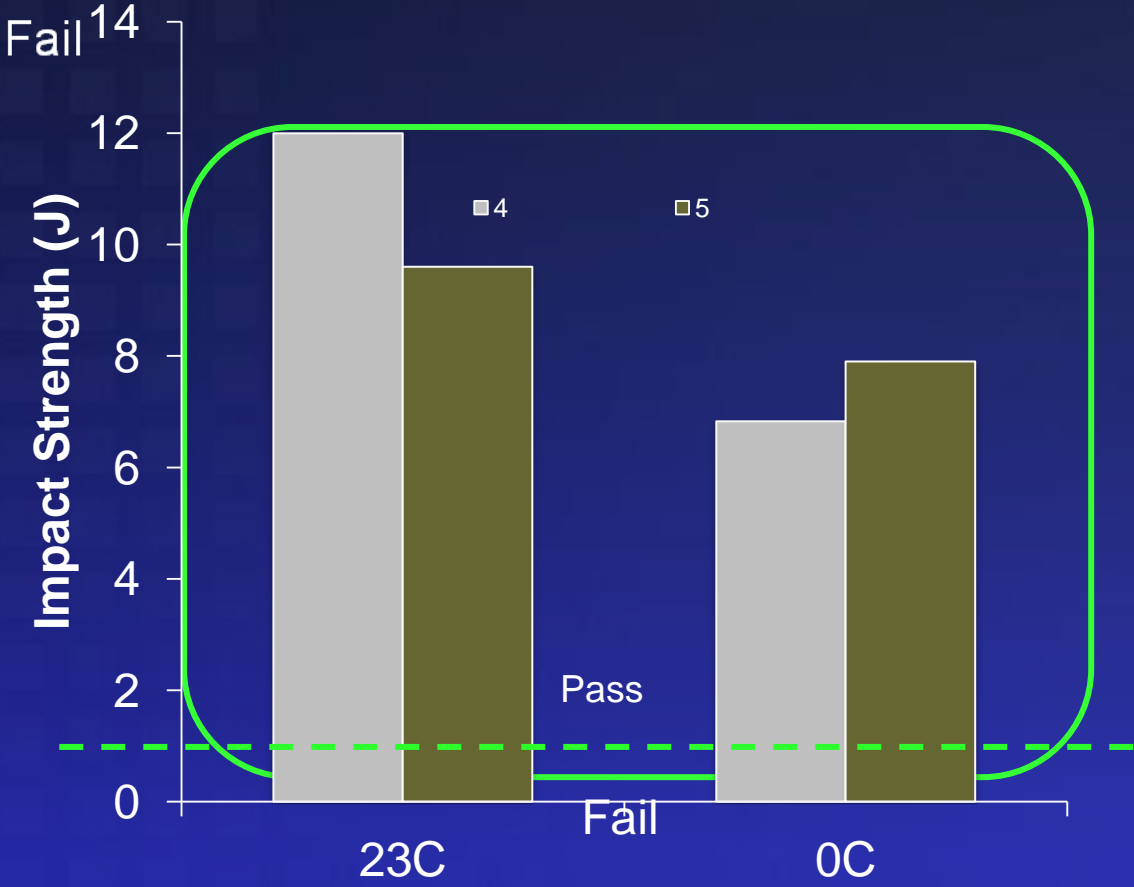

Abrasion resistance

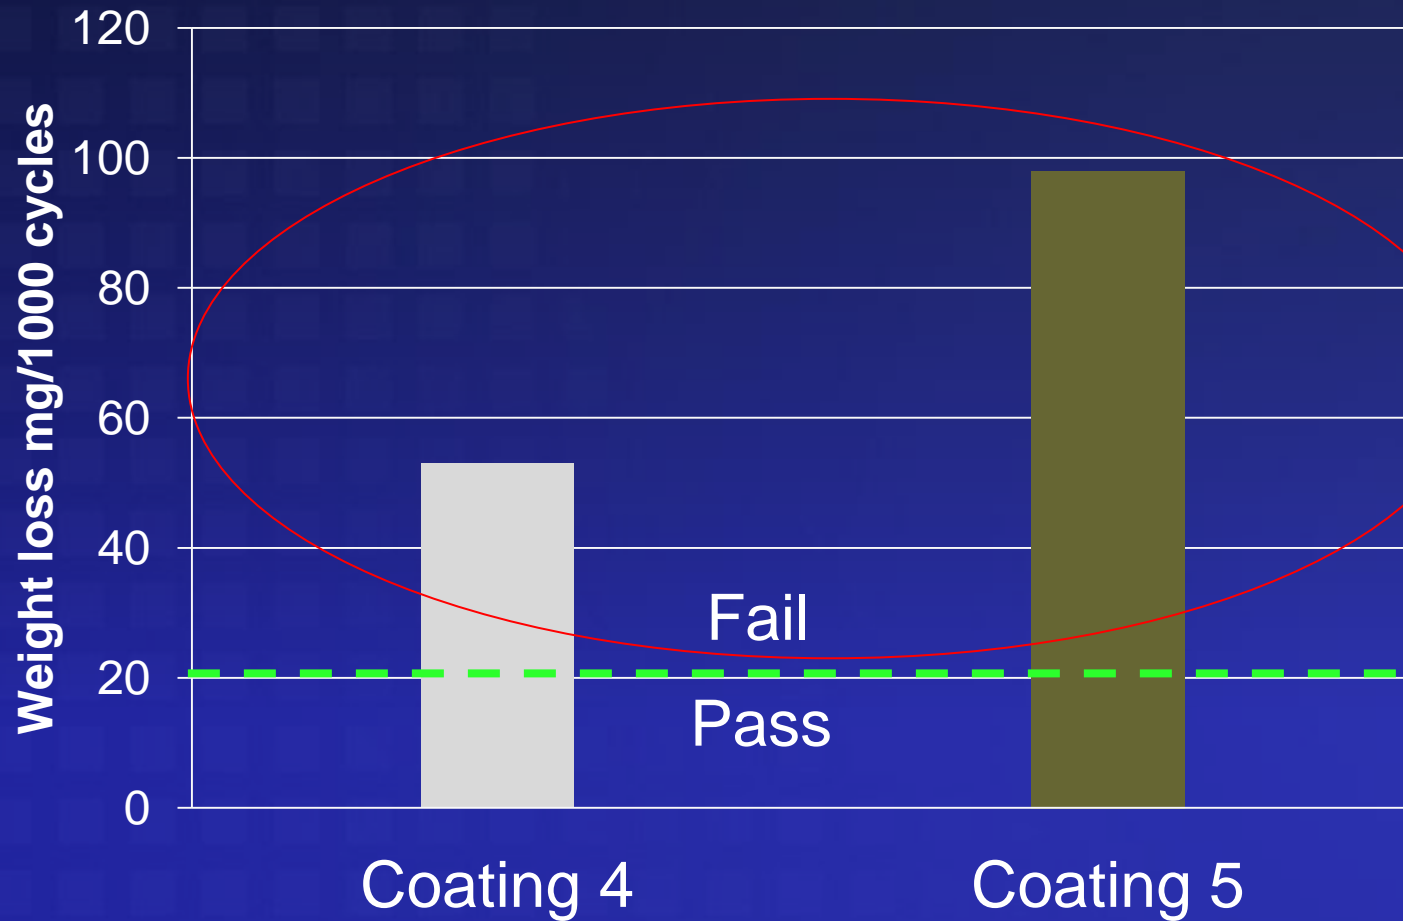

Chemical Resistance



Samples were exposed to test media for 90 days and then to autoclave testing and rating.

Test Media

HCl aq. pH 2.5-3.0

HF aq. pH 2.5-3.0

H₂SO₄ aq. pH 2.0

NaCl and H₂SO₄ aq. 100,000 ppm
chlorides pH 3.0

10 % NaCl aq.

Distilled water

Toluene

Autoclave conditions:

- 93°C, 2000 psi/14MPa
- 50% of sample in 5% NaCl aq.
- Gas: 0.5% H₂S, 5% CO₂, 94.5% CH₄
- 48 Hours
- Rapid decompression at 47°C (after 4 hours cooling)

Coating 4: no visible degradation to chemicals except surface uniformity in toluene; after autoclave no adhesion loss but severe colour change and slight surface roughness; also in toluene F#4 blisters at gas-water interface - **PASS**

Coating 5: no visible degradation to chemicals or autoclave except severe colour change in latter and slight adhesion loss in gas phase - **PASS**


DSC

Tests on the samples as received resulted in T_g values NOT ≥ 10°C above max. operating temp.

BUT additional tests on samples after hot water immersion showed increases in T_g values

Sample ID			T _g (°C)
Coating 5	Sample before hot water test	#1	78
		#2	78
	Sample after hot water test	S1	119
		S3	117
	Sample stored 90 days at 23 °C		
Coating 4	Sample (before hot water test)	#1	76
		#2	77
	Sample after hot water test	HWR2	92
		HWR4	93
	Sample stored 90 days at 23°C		

Coefficient of linear thermal expansion (CLTE)

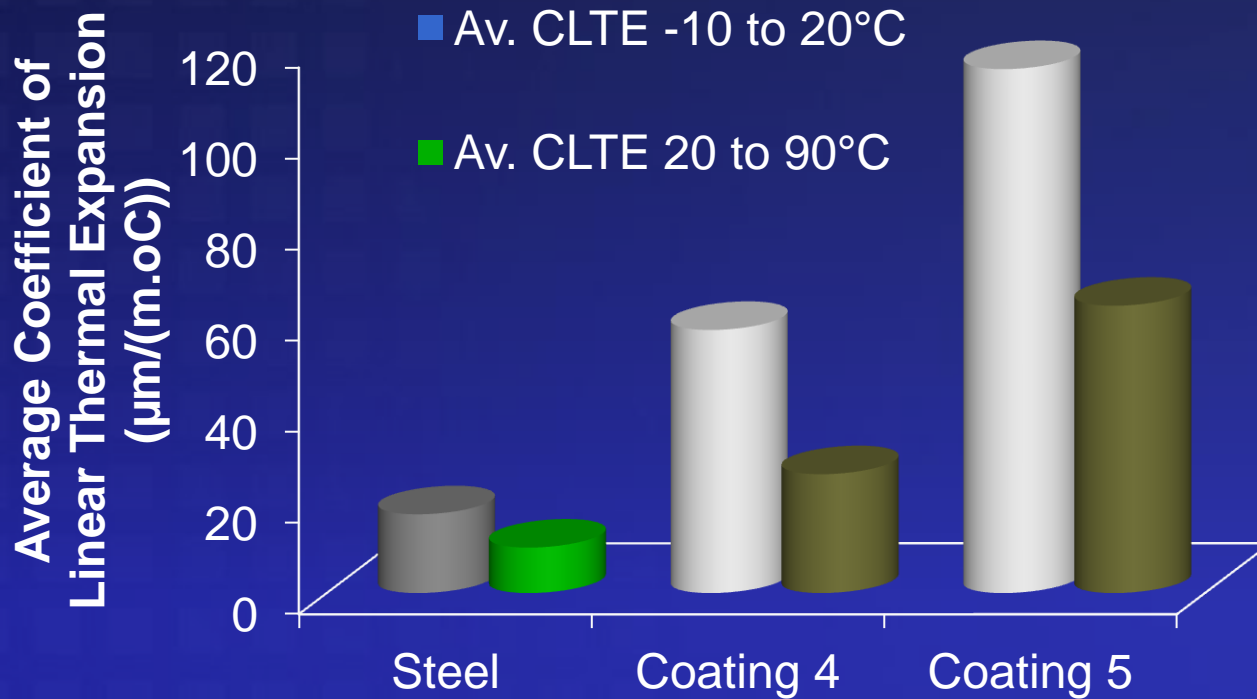

Coatings 4 & 5 Qualification Tests



- Both good BUT did not meet all criteria, differences!
- Both had good hardness, adhesion, and resistance to impact, penetration, chemicals, hot water, salt fog, autoclave and gas pressure variation.
- Lower than required Tg but this increased after 85°C immersion, especially for Coating 4.
- Lower than required abrasion resistance and flexibility.
- Coating 5 more flexible than Coating 4.
- Coating 4 better WVT than Coating 5.
- Coating 5 passed water absorption test but Coating 4 showed increasing absorption at 85°C up to full 90 days of test.
- Coating 4 had lower CLTE (better = closer to that of steel)
- Coating 4 showed some chemical attack in CD test.

Conclusions



Both Coatings 4 and 5 showed good performance in the qualification tests but did not meet all the specification criteria.

Ultimately based on performance in all the tests it was decided to include Coating 5 in field trials that are now starting.